

# Mechanical Properties of Rice Husk /Carbon Black Hybrid Natural Rubber Composite

P. E. Imoisili<sup>1,\*</sup>, K. O. Ukoba<sup>1</sup>, I. T. Adejugbe<sup>1</sup>, D. Adgidzi<sup>2</sup>, S.O.O. Olusunle<sup>1</sup>

1. Engineering Materials Development Institute P.M.B. 611, Akure. Ondo state, Nigeria
2. Agricultural Engineering Dept., Federal University of Technology, Minna, Nigeria

\* E-mail of the corresponding author: [patrickehis2002@yahoo.com](mailto:patrickehis2002@yahoo.com)

## Abstract

The mechanical and end use properties of natural rubber reinforced rice-husk/Carbon Black hybrid filler, was investigated. Hybrid filler were used to prepare a natural rubber vulcanizate in order to determine testing data for the mechanical properties of the compound. In the sample preparation, six levels of filler loading were designed, which include variation in carbon black volume content. Tensile strengths, compression set, abrasion resistance, and Hardness, of the vulcanizate shows improvement with increase in carbon black content, while elongation at break shows decrease with increase in carbon black content. The flex fatigue shows great improvement. Thus rice-husk/Carbon Black Hybrid filler can be utilized as reinforcing filler in the rubber industry, where specific end-use property of a rubber product is required.

**Keywords:** Hybrid, Filler, Natural rubber, Rice husk, Carbon black

## 1. Introduction

In an agrarian economy, especially in developing countries like Nigeria, harvests seasons are often accompanied with tones of residues that constitute, in mist case environmental menace and some cases hazards. Many of these wastes are fibrous in natural; this class of materials could be utilized in the design and development of new polymeric composite materials as filler. These natural fillers when used as reinforcing fillers is not only inexpensive but also able to minimize the environmental pollution caused by the characteristic biodegradability (Premalal *et al* 2002, Han-Seung Yang *et al* 2004)

In the compounding of rubber products, fillers are major additives. Incorporation of such additives into the rubber matrix enhances properties such as tensile strength, modulus, tear strength, abrasion resistance, stiffness and possibility. The cost of the manufactured rubber product is also significantly reduced (Okieimen and Imanah 2003). In the vulcanization of rubber, carbon black is the main filler in use, However, because of the origin of carbon black from petroleum, carbon black causes pollution, and gives the rubber a black colour. The filler is also costly (Isaac and Augustina 2011)

Different materials have been used to reinforce natural and synthetic rubber such as clay (Kim *et al* 2006),organo clay (Arroyo *et al* 2003), coal shale-based fillers (Zhao and Xiang 2004), synthetic precipitated amorphous white silica nanofiller.(Ansarifar *et al* 2006), recycled rubber powder (Ismail *et al* 2002), graphite (Yang *et al* 2006). Agricultural by-products as fillers has also been investigated, this included banana peel, rice husk, spent mango, bean seed skin and groundnut shell (Adeosun 2002), cocoa pod and rubber seed shell (Okieimen and Imanah 2003 ), and short pine apple leaf fiber (Lopattananon *et al* 2006), ash rice husk (Ismail *et al* 2001). In addition, the processing of these composite materials is flexible, economical, and ecological and it is possible to use the same machinery employed with other traditional fillers.

In this present work the use of rice husk and carbon black N330 grade as reinforcement in natural rubber is reported, the objective, is to investigate the effect of rice husk/ carbon black (N330) hybrid filler on the mechanical properties of natural rubber composite.

## 2. Materials and Methods

Rice husk (RH) was obtain from a local rice mill in south western Nigeria, natural rubber (TSR 5) was obtain from NR processing factory Utagbo-Nno Delta state Nigeria, while Carbon black (CB) (N330 grade) was obtain from Warri Refinery And Petrochemical Company, Warri Nigeria. Compounding ingredients were of commercial grade and were used as obtained

### 2.1. Composite Preparation

Rice husk (RH) was washed and dried at 105°C for 24hr to adjust its moisture content and then stored over desiccant in sealed containers, the sample was grinded into powder with the use of an electric blender. The grinded powder was later sieved with BS/ISO 3310 into particle size of 38 µm. The natural rubber (NR) was masticated with other compounding ingredients in a laboratory two-roll mixer, as showed in table 1. Filler content was maintain at 50pph, six different test samples were prepared, the volumetric relation between rice husk and carbon black was modified according to the following composition

- a) 100% carbon black and 0% Rice husk

- b) 90% carbon black and 10% Rice husk
- c) 80% carbon black and 20% Rice husk
- d) 60% carbon black and 40% Rice husk
- e) 50% carbon black and 50% Rice husk
- f) 0% carbon black and 100% Rice husk

## 2.2. Determination of Vulcanizate Properties

The curing of test pieces was done by compression molding. The curing was carried out at 140 °C, the Tensile strength modulus and elongation was done as describe in ASTM D412-87 (Method A), using the Instron universal testing machine model 4301. Abrasion resistance was done using test method for Abrasion resistance DIN to ISO 4649 Akron to BS 903 part 49 (Method C), using croydon Akron-Wallace Abrada with serial no 0840251. Compression set was done as described in. ASTM D395, using a Wallace compression test equipment with serial no 0840522. Hardness test was done as specified in ASTM 1415 using the Wallace hardness tester model C8007/25. The measurement of Flex fatigue was done as describe in ASTM D430, using the Wallace De-Mattia flex machine.

## 3. Results and Discussions

Result of mechanical properties of the composite figure 1-4, reviles that increase in carbon black content yield an increase in tensile strength, modulus, abrasion resistance and hardness, this can be attributed to increase interaction between filler and rubber matrix, filler dispersion, and high surface area of N330 carbon black . It is well known that natural rubber forms a strong adsorptive bond with carbon black (Ismail et al 2001).

Figure 5 shows, effect of carbon black content on Elongation at break [EB]. Generally, the addition of fillers into natural rubber leads to decreases in EB of rubber vulcanizate, irrespective of whether the filler is reinforcing or inert, this trend, decreases in EB with increasing carbon black filler content may be due to the non-stiffening of the rubber chains, and hence, non-resistance to stretch when strain is applied.

Analyzing the result in figure 6, decrease in flex fatigue has been explained in terms of adherence of the filler to the polymer phase leading to the stiffening of the polymer chain and hence resistance to stretch when strain is applied. (Lopattananon et al 2006 ), in this case, as carbon black content increases there is reduce stiffening of polymer chain and resistance to stretching and thus an improve fatigue resistance.

## 4. Conclusion

Mechanical properties of rice husk/Carbon Black Hybrid filler reinforced natural rubber compounds has been studied. An increased in N330 Carbon Black content in the hybrid fillers has yield an increased in tensile strength, modulus hardness and abrasion resistance of the compounds. Elongation at break shows decrease, while the fatigue resistance of the compound shows considerable improvement. Thus rice husk/carbon black hybrid filler can be used as reinforcement in natural rubber compound, were specific end use properties are require.

## References

- Adeosun. B. F. (2002) Mechanical and Rheological Properties of Natural Rubber Composites Reinforced with Agricultural Waste. *Nigerian Journal of Polymer Science and Technology*, 1, (1), 58-62.
- Ansarifar. A., Shiah. S. F. & Bennett. M. (2006). Optimizing the Chemical Bonding between Silanised Silica Nanofiller and Natural Rubber and Assessing Its Effects on the Properties of the Rubber,” *International Journal of Adhe-sion and Adhesives*, 26, (6), 454-463.
- Arroyo. M., Lopez-Manchado M. A. & Herrero. B., (2003) Organo-montmorillonite as Substitute for Carbon Black in Natural Rubber Compounds,” *Polymer*, 44, (8), 2447-2453.
- Han-Seung Yang , Hyun-Joong Kim , Jungil Son , Hee-Jun Park ,Bum-Jae Lee , & Taek-Sung Hwang (2004). Rice-husk flour filled polypropylene composites; mechanical and morphological study. *Composite Structures* 63, 305–312
- Isaac Ogbennaya Igwe, & Augustina Adanna Ejim (2011) Studies On Mechanical and End-Use Properties of Natural Rubber Filled With Snail Shell Powder. *Materials Sciences and Application*, 2, 802-810
- Ismail, H., Mega, L.; Abdul-Khalil, H. P. S. (2001). Effect of a Silane coupling agent on the properties of white rice husk ash polypropylene/Natural Rubber Composite. *Polymer International*, 50, (5). 606-611.
- Ismail. H., Nordin R., & Noor, A. M. (2002) Cure Characteristics, Tensile Properties and Swelling Behaviour of Recycled Rubber Powder-Filled Natural Rubber Compounds *Polymer Testing*, 21, (4), 565-569.
- Kim. M., Kim. D., Chowdhury. S. R., & Kim G. (2003) Melt-Compounded Butadiene Rubber Nanocomposites with Improved Mechanical Properties and Abrasion Resistance, *Journal of Applied Polymer Science*, 102, (3), 2062-2066.
- Lopattananon N., Panawarankul K., Sahakaro K., & Ellis B. (2006). Performance of Pineapple Leaf Fibre-Natural Rubber Composites: The Effect of Fibre Surface Treatments. *Journal of Applied Polymer Science*. 102,

1974-1984.

Okieimen F. E. & Imanah J. E. (2003).The characterization of agricultural waste product as filler in NR formulations. *Nigeria journal of polymer science and technology*; 3. (1), 178-240

Premalal HGB, Ismail H, & Baharin A.(2002) Comparison of the mechanical properties of rice husk powder filled polypropylene composites with talc filled polypropylene composites. *Polym Testing*; 21 (7):833–839.

Yang J., M. Tian M., Jia Q, Zhang L. & X. Li. (2006). Influence of Graphite Particle Size and Shape on the Properties of NBR. *Journal of Applied Polymer Science*, 102, (4), 4007-4015.

Zhao. M & Xiang Y. (2004). Natural Rubber Vulcanizate Reinforced by Modified Coal shale-Based Fillers. *Journal of Applied Polymer Science*, 93, (3), 1397-1400.

**Table 1: Compounding recipe.**

Ingredients	pphr
Natural Rubber	100
Sulphur	2.5
Zinc Oxide	5
CBS	2
TMQ	1
Stearic Acid	2
Processing oil	2.5
Filler	50

\*pphr-part per hundred rubber

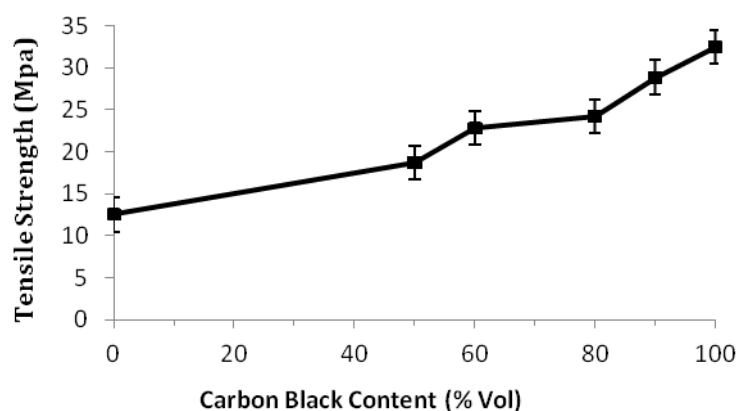


Figure 1. Tensile strength of the composite in relation to Carbon Black Content

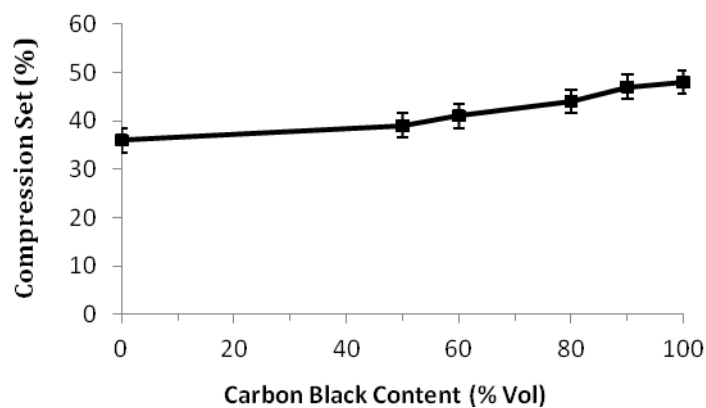


Figure 2. Compression set of the composite in relation to Carbon Black Content

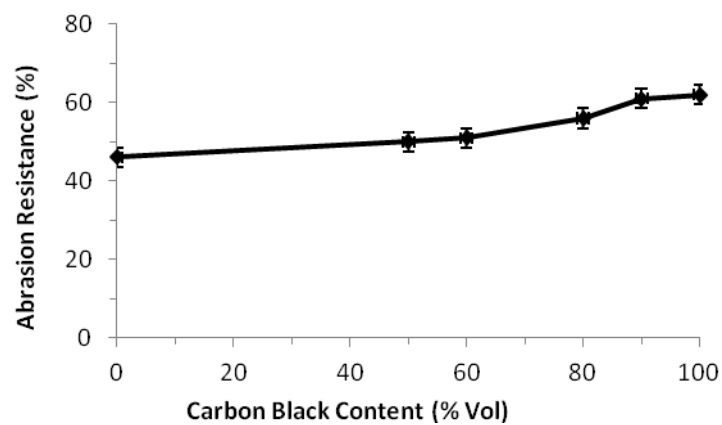


Figure 3. Compression set of the composite in relation to Carbon Black Content

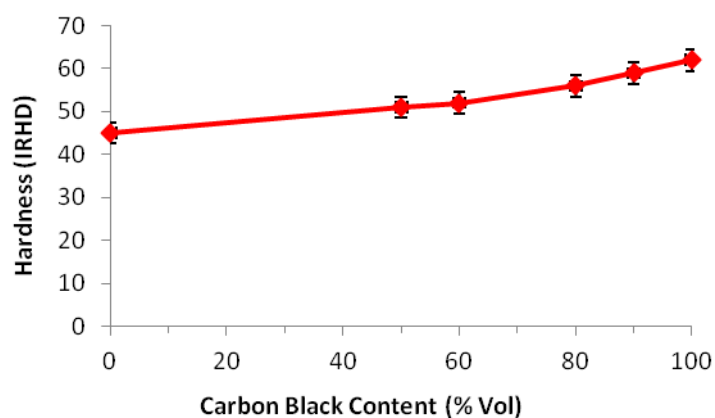


Figure 4. Hardness of the composite in relation to Carbon Black Content

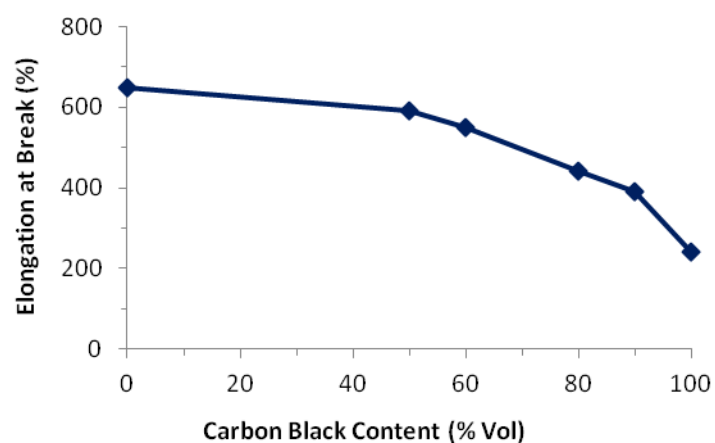


Figure 5. Elongation at Break of the composite in relation to Carbon Black Content

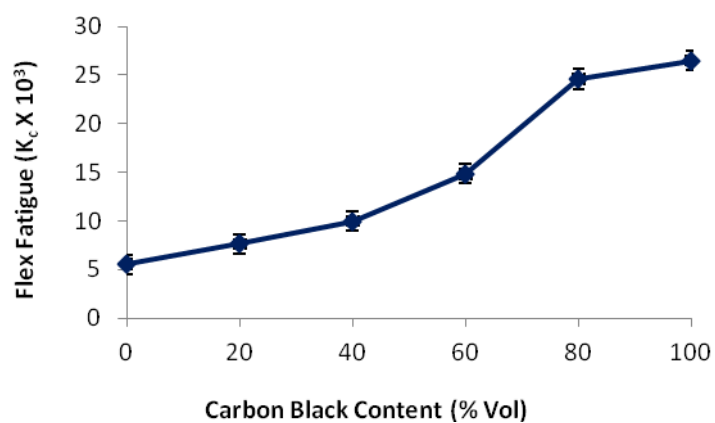


Figure 6. Flex Fatigue of the composite in relation to Carbon Black Content

This academic article was published by The International Institute for Science, Technology and Education (IISTE). The IISTE is a pioneer in the Open Access Publishing service based in the U.S. and Europe. The aim of the institute is Accelerating Global Knowledge Sharing.

More information about the publisher can be found in the IISTE's homepage:

<http://www.iiste.org>

## CALL FOR PAPERS

The IISTE is currently hosting more than 30 peer-reviewed academic journals and collaborating with academic institutions around the world. There's no deadline for submission. **Prospective authors of IISTE journals can find the submission instruction on the following page:** <http://www.iiste.org/Journals/>

The IISTE editorial team promises to review and publish all the qualified submissions in a **fast** manner. All the journals articles are available online to the readers all over the world without financial, legal, or technical barriers other than those inseparable from gaining access to the internet itself. Printed version of the journals is also available upon request of readers and authors.

## IISTE Knowledge Sharing Partners

EBSCO, Index Copernicus, Ulrich's Periodicals Directory, JournalTOCS, PKP Open Archives Harvester, Bielefeld Academic Search Engine, Elektronische Zeitschriftenbibliothek EZB, Open J-Gate, OCLC WorldCat, Universe Digital Library, NewJour, Google Scholar

